

Dolfini A, Crellin RJ. [Metalwork wear analysis: The loss of innocence](#). *Journal of Archaeological Science* 2016, 66, 78-87.

Copyright:

© 2016. This manuscript version is made available under the [CC-BY-NC-ND 4.0 license](#)

DOI link to article:

<http://dx.doi.org/10.1016/j.jas.2015.12.005>

Date deposited:

26/01/2016

Embargo release date:

14 January 2017



This work is licensed under a [Creative Commons Attribution-NonCommercial-NoDerivatives 4.0 International licence](#)

Metalwork Wear Analysis: The Loss of Innocence

Andrea Dolfini¹ and Rachel J. Crellin²

¹Newcastle University

School of History, Classics and Archaeology, Armstrong Building, Newcastle University,
Newcastle upon Tyne, UK, NE1 7RU.

andrea.dolfini@ncl.ac.uk

²University of Leicester

School of Archaeology and Ancient History, University Road, Leicester, UK, LE1 7RH.

rjc65@le.ac.uk

Corresponding Author

Images



Fig. 1 – Combat tests with replica Bronze Age swords and shields. Experiential tests of this kind have led to a wholesale reappraisal of the fighting potential and uses of prehistoric metal weaponry (from Molloy 2009).

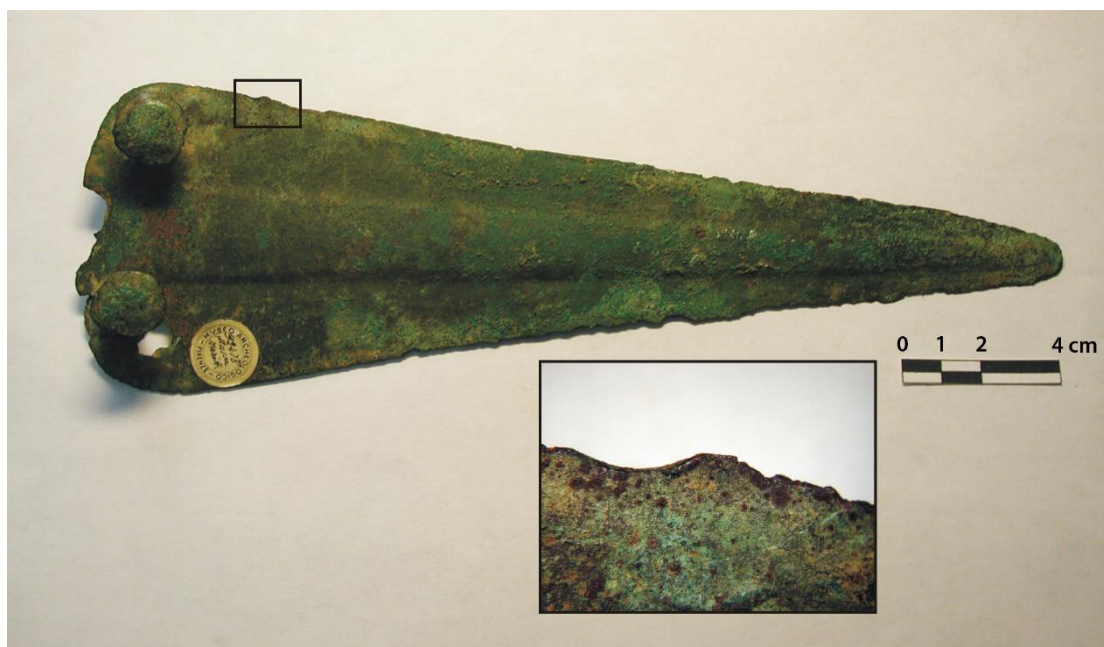


Fig. 2 – Prehistoric halberd blade from Italy. Prehistoric halberds from Europe often display distinctive marks on the cutting edges (see inset, x12 magnification), which are interpreted as evidence of blade-on-blade strike in combat encounters (photo: A. Dolfini, reproduced by courtesy of the Soprintendenza per i Beni Archeologici della Toscana).



Fig. 3 – Early Bronze Age Flat Axe from the Manx Museum on the Isle of Man. The photo and micrograph showing striations from both wear and re-sharpening to the blade. (photo: R. Crellin, with permission of Manx National Heritage).



Fig. 4 – Newcastle student Joshua Desrosier fells a birch tree with a replica Middle Bronze Age palstave. Designing meaningful experiments with replicas forces researchers to make educated guesses regarding construction technology and the uses of prehistoric objects (photo: A. Dolfini).

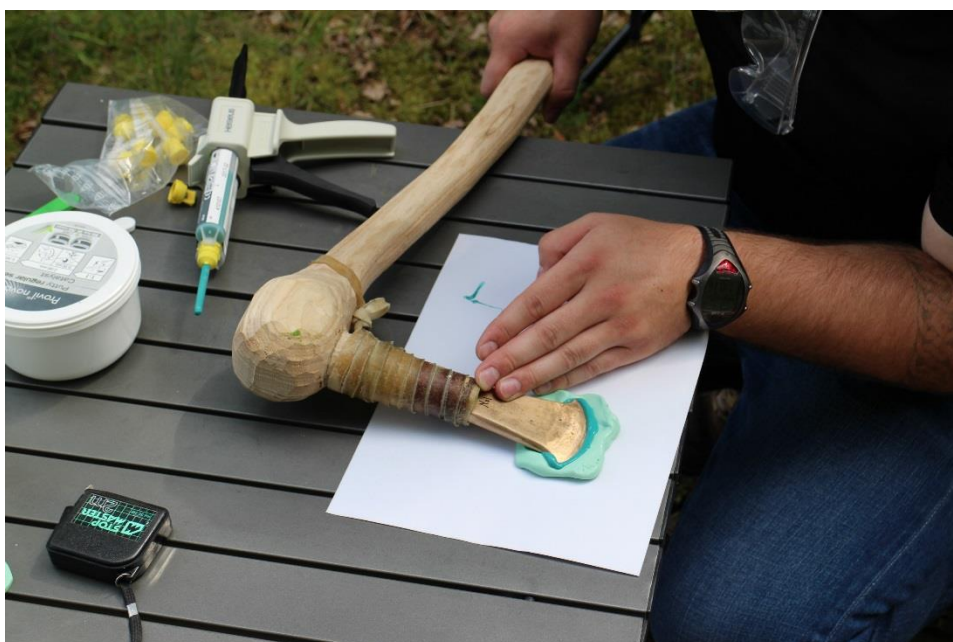


Fig. 5 – Taking a cast of an experimental axe blade using high-precision impression material (photo: A. Dolfini).

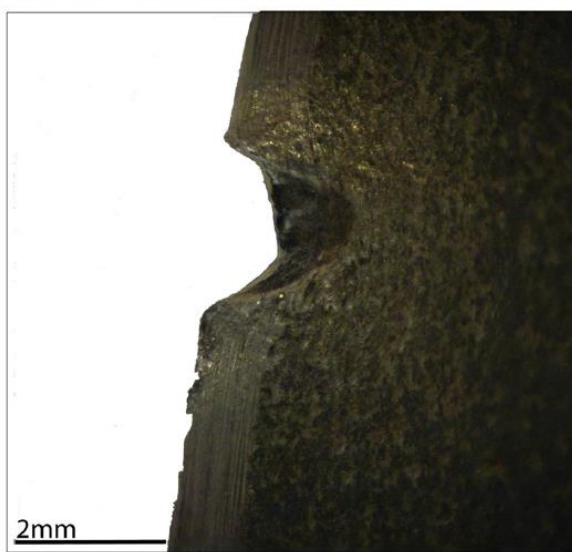
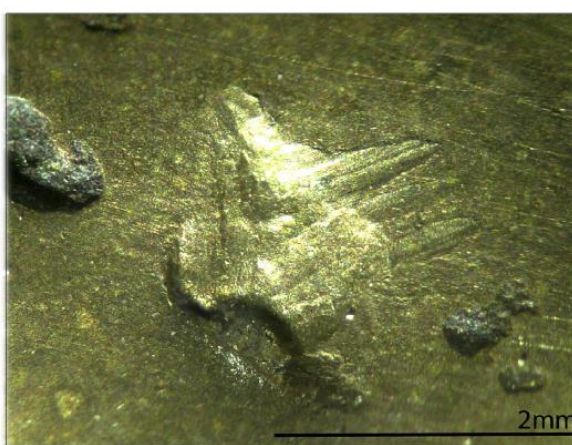
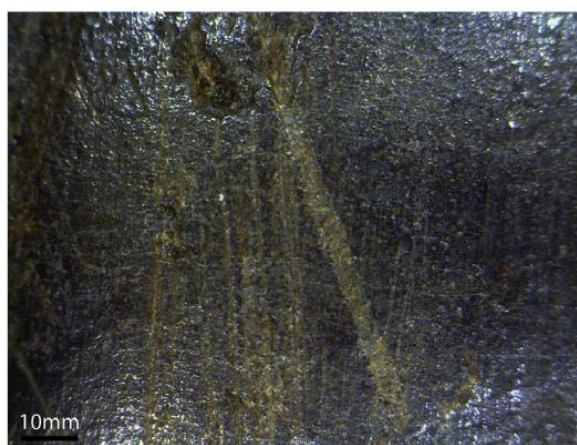


Fig. 6 – Wear marks on a range of copper-alloy objects. *Top left*: Use-wear marks on the surface of a Late Bronze Age sword from the Yorkshire Museum of Archaeology (bar length – 10mm, photo: R. Hermann). *Top right*: Spear stab mark on the surface of a replica bronze shield (bar length – 2mm; photo: R. Crellin). *Lower left*: Bending and notching to the blade of a flanged Early Bronze Age axe from the Manx Museum, Isle of Man (bar length – 2cm, photo: R. Crellin, with permission of Manx National Heritage). *Lower right*: Notch to the blade of a replica spearhead caused by a sword blade (bar length – 2mm, photo: R. Crellin).

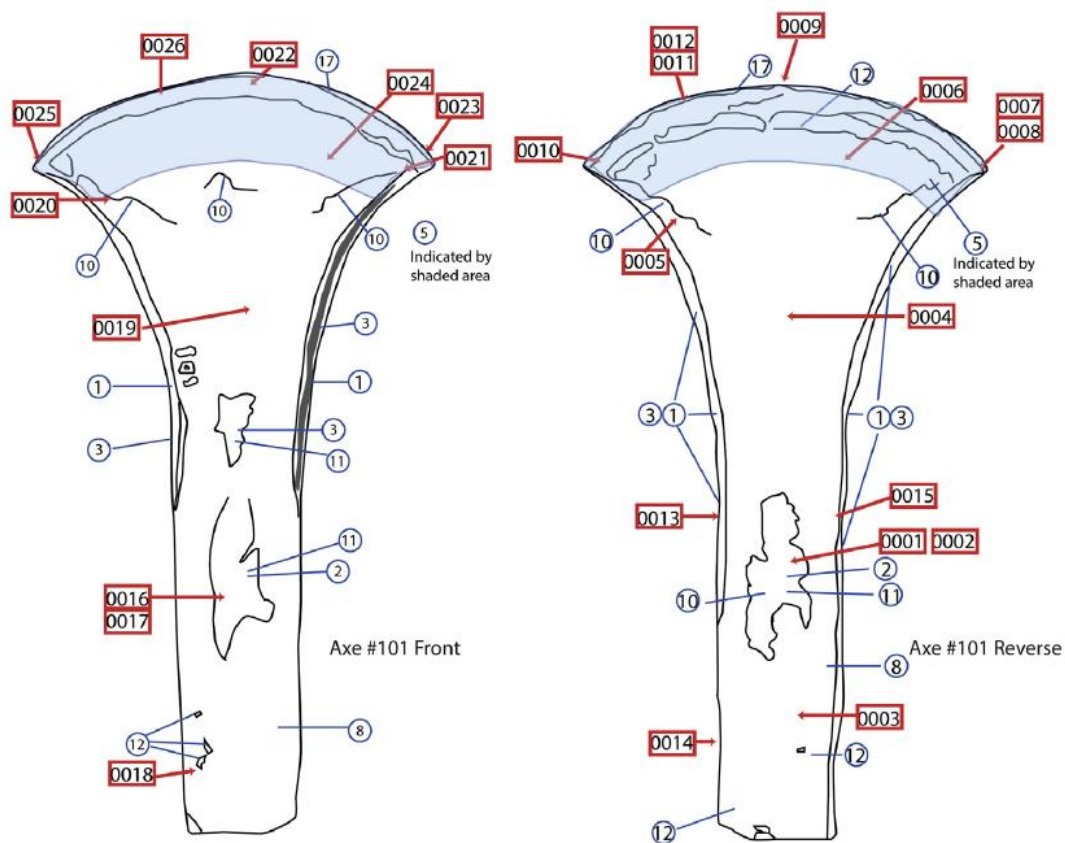


Fig. 7 – Annotated digitised sketch of a replica axe. Figures in blue circles relate to observed wear marks, figures in red boxes indicate the position and number of associated micrographs (illustration: R. Crellin).

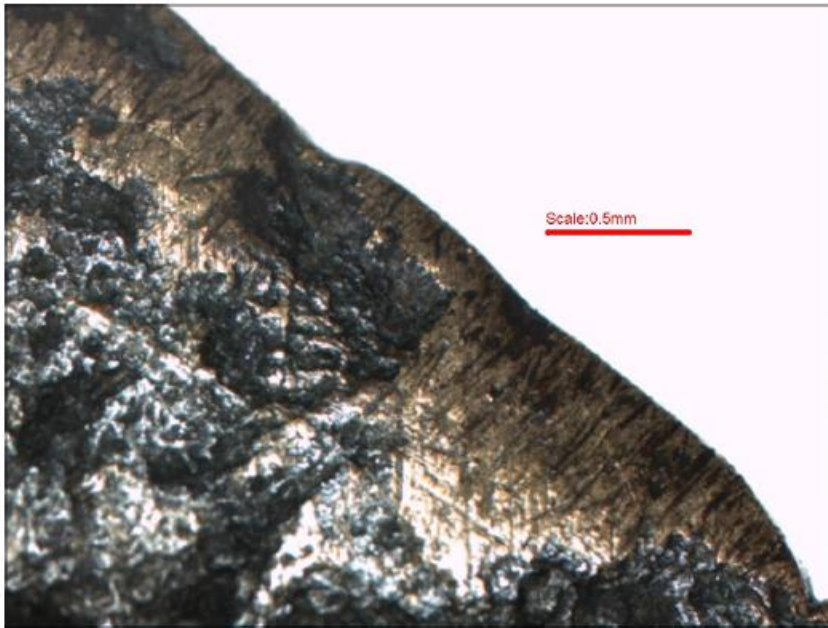


Fig. 8 – Short perpendicular striations associated with localised polish on the cutting edge of a copper-alloy axe-heads from the Tyne and Wear Archives and Museums collections, Newcastle upon Tyne. Although frequently observed, the use-related polish found on ancient metalwork has hitherto received little attention from analysts (bar length: 0.5mm; photo: J. Desrosier, by courtesy of the Society of Antiquaries of Newcastle upon Tyne).



Fig. 9 – Field tests with replica swords within the Newcastle Bronze Age Combat project. Problem-oriented test design and a clear methodology are essential components of any experiments aiming to understand wear formation processes (photo: D. Horan).

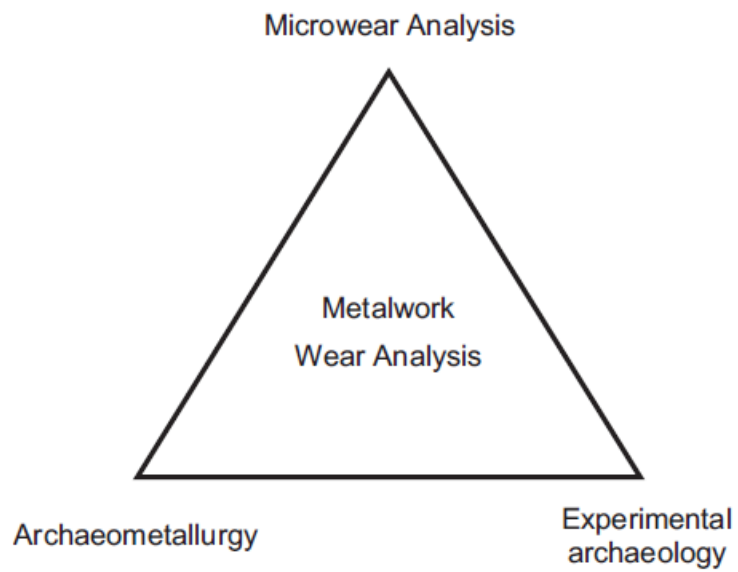


Fig. 10 – It is maintained in this article that metalwork wear analysis ought to position itself at the disciplinary intersection between microwear analysis, archaeometallurgy, and experimental archaeology (drawing: A. Dolfini).

Abstract

Metalwork wear-analysis has now been practised for almost two decades. In this paper the authors present the achievements of the discipline and critically assess the methodologies currently applied by practitioners. Whilst the achievements and contributions of the discipline to the wider study of archaeology, and to European prehistory in particular, are numerous, it is argued that an increase in scientific rigour and a focus on addressing limitations and open problems is required if metalwork wear-analysis is to flourish as a scientific field of research. Experimentation with higher magnifications and novel microscopic techniques is encouraged, alongside more standardised and explicit analytical protocols for analysis. More details and targeted descriptions of analytical protocols for experimental work are required: experiments must be designed to answer specific questions and address lacunas in knowledge. While at present the majority of practitioners focus their analyses on copper alloys from European prehistory, and most specifically from the Bronze Age, the authors suggest that a far wider range of materials are suitable for analysis including copper alloys from the Americas and iron alloys from historic and ethnographic collections. Expanding the range of materials studied would open the field up and give it far wider relevance to archaeology and material culture studies. Finally, it is argued that the discipline will advance more quickly if practitioners share their reference collections and databases of experimental marks digitally. The authors suggest that the creation of digital reference collections, open to all, would provide metalwork analysts with the opportunity to lead related fields of research such as lithic microwear and residue analysis, where individual reference collections are the norm and cross-comparability of analysis is therefore hindered.

Keywords

metalwork wear analysis; use-wear analysis; microwear analysis; traceology; metallurgy; copper-alloy; experimental archaeology

1.1 Introduction

After nearly two decades of sustained research and experimentation, the wear analysis of archaeological metals is close to becoming a full-grown field of archaeological science. The subject initially emerged at the disciplinary nexus between lithic microwear studies and archaeometallurgy, and soon acquired its own distinctive goals, methods, and approaches. As new classes of bronze objects were examined microscopically and new traces were identified, however, new problems also emerged, which have exposed the limits of the discipline. In particular, a disconnection of sorts has emerged between metalwork and lithic wear studies owing to the oft-diverging research interests of their practitioners, the practical and material differences between the objects of study, and the lack of formal training in microwear analysis by many a metalwork specialist. As this position appears increasingly untenable, it is now urgent to reassess the developmental trajectory, methodology, and limitations of metalwork wear analysis in order to ensure its steadfast growth for years to come.

The aim of this article is to conduct this reassessment. The authors firmly believe that metalwork wear analysis is close to outgrowing the exciting, if rather disorderly, stage that

characterises all pioneering fields of research, and is now coming of age. However, to mature as an independent branch of archaeological science, the discipline needs to lose its early innocence (*sensu* Clark, 1973). This minimally involves the development of a more reflexive approach to artefact experimentation and analysis, a broadly agreed strategy for filling its knowledge gaps, and a self-conscious decision as to where the subject is to stand in relation to lithic microwear analysis, archaeometallurgy, and experimental archaeology. In this article we explain how these goals may be achieved. After discussing issues of definition, we outline a brief history of the discipline, review its analytical methods, and present a number of key suggestions for its future development. We sincerely hope that our work will trigger a broader debate concerning the future of metalwork wear analysis and how it can reach disciplinary maturity.

2.1 Issues of Definition

Various terms have been employed to define the branch of wear studies dealing with metalwork. *Use-wear* (or *usewear*) *analysis* is the one used most widely in the literature (e.g. Dolfini, 2011; Gordon, 1985; Kampaus, 2006; Kienlin and Ottaway, 1998). The term, borrowed from lithic microwear studies, refers to the wear visible on the edges and surfaces of an object, which is caused by use (1) (Hayden, 1979; Marreiros et al., 2015; Odell, 2004). The limits of this definition become apparent upon considering that many of the traces observed on metals are not linked to artefact utilisation, but to manufacturing and post-depositional processes (Gutiérrez-Sáez and Martín-Lerma, 2015; Roberts and Ottaway, 2003). *Traceology*, a term similarly borrowed from lithic wear research, refers to the study of any traces visible on ancient tools (Fullagar and Matheson, 2014: 7063). Its use would avoid the implication that wear was only generated by use, or is solely found on the 'working parts' of the objects. The term, however, is normally used in lithic studies to encompass residue analysis, and is therefore too broad at present as residue analysis is wholly marginal within metalwork studies. *Functional analysis* has some currency in lithic wear research, but has rarely been employed outside it. Although used synonymously with use-wear analysis, it may in fact imply the application of methods and approaches lying outside the discipline (e.g. artefact classification and experimental archaeology). Furthermore, as with the term use-wear, it does not encompass the range of production and post-depositional marks observed on objects, and is also rather vague (Donahue, 1994: 156).

We propose here that the discipline be renamed *metalwork wear analysis*. Although this term has never been used in the context of metal traceology, it presents a number of distinctive advantages. Firstly, it does not solely focus on the analysis of use-related traces, and does not imply that certain portions of the object may carry a higher informative value than others. Yet it is close enough to the now-prevalent 'use-wear analysis' to be recognisable by both practitioners and the wider research community. Secondly, it explicitly refers to the methods and approaches of archaeological wear research while also capturing the specificities of the subject, e.g. the prevailing utilisation of low-power microscopy (see 3.1 and 4.2.3). Thirdly, it suggests that the general principles of the discipline are experimentally based and broadly derived from two areas of engineering research: tribology and fracture mechanics (Donahue, 1994). Presently, this is the term that best captures the

distinctiveness of the subject whilst explicating its close relationship with lithic microwear studies.

3.1 Metalwork Wear Analysis: History and Research Advances

Metalwork wear studies developed much later than lithic microwear research despite Semenov's early work on metal tools (Semenov, 1964). Such a late development has been ascribed to a number of reasons including the fear that recycling, manipulation, re-sharpening and corrosion would seriously limit the potential of metalwork wear analysis (Roberts and Ottaway, 2003: 120). It has also been attributed to long-standing preoccupations with typology as the chief avenue for assessing the functionality of ancient bronzes (Gutiérrez-Sáez and Martín-Lerma, 2015: 171). It may perhaps be added that researchers, and especially the students of the European Bronze Age, were for a long time reluctant to consider that our prehistoric past might have been a violent one (Keeley, 1996); hence their hesitation to search bronze weapons for combat marks or to test their use-value experimentally. The combined influence of these factors was ultimately responsible for the delayed emergence of metalwork wear analysis *vis-à-vis* lithic traceology.

The examination of use-related marks on prehistoric and historic copper alloys was pioneered from the late 1970s by a small number of European and American scholars, who appear to have been largely unaware of each other's work. In Europe, Kristiansen (1978; 1984; 2002) assessed the functionality of Bronze Age swords using interdisciplinary approaches that encompassed, but were not limited to, the microscopy-enhanced observation of large assemblages of objects, while Schauer (1979) trialled the investigation of use marks on spear-heads. In America, Penman (1977) tested the potential of wear analysis on artefacts from the Old Copper culture, while Gordon (1985) studied indigenous bronze tools from Machu Picchu using a novel combination of microscopy and metallurgical analysis. These early studies may be commonly defined by (a) the non-specialist background of the scholars, none of whom had any formal training in lithic microwear analysis; (b) a certain lack of methodological sophistication, evident for example in the absence of experimentation with replica objects; and (c) their eclectic approaches, which employed optical microscopy within a broader spectrum of archaeological and analytical methods.

Pioneering studies of this kind were carried out until the late 1990s (e.g. Bridgford, 1997; 2000; Wall, 1987), when Kienlin and Ottaway (1998) first proposed a rigorous methodology for the wear analysis of copper-alloy objects, which deliberately drew on lithic microwear research. Their ground-breaking investigation of prehistoric axe-heads encompassed the following steps:

- (1) field tests with replica axes in order to understand wear formation processes;
- (2) taking dental casts of the cutting edges of experimental and prehistoric axe-heads;
- (3) examining the dental casts using a low-power stereo-microscope in order to interpret ancient wear patterns by comparison with the experimental ones.

Kienlin and Ottaway's research marked the birth of modern metalwork wear analysis, and their 'classic' three-step approach has since been widely employed, albeit with some adaptations (see 4.1).

As most researchers were interested in prehistoric copper alloys from Europe, the new discipline made significant inroads into Copper Age and Bronze Age studies. In particular, four classes of artefact were afforded the greatest attention: swords, shields, spears, and halberds. Kristiansen and Bridgford's early work on swords was taken forward by Molloy (2007; 2008; 2010; 2011), who advocated a martial-arts approach to the study of these iconic prehistoric weapons. This was based on integrated wear analysis of archaeological objects and field experiments with replica swords, in which he tested the combat potential of the weapons in staged duels (Fig. 1). He was able to show that the alleged division between Middle Bronze Age 'rapiers' and Late Bronze Age 'cut-and-thrust' swords, which had long dominated Bronze Age studies, is incorrect as both types of weapon are suitable for thrusting and slashing attacks, and both display similar combat marks on their cutting edges. Other researchers concentrated on different problems. For example, Quilliec (2008) investigated both combat and destruction marks on a sample of swords from Atlantic Europe, paying special attention to any contextual differences which could shed light on codified practices of use and deposition. In a similar vein, Mödlinger (2011) integrated the wear analysis of central European swords with chemical analysis, x-raying, and 3D computer tomography – an approach that allowed her to unlock the complete life-cycle of the objects from production to deposition. Overall, these scholars revealed that Bronze Age swords had complex object biographies (*sensu* Gosden and Marshall, 1999), which often included use in combat encounters.

The innovative results obtained by sword wear analysis were further supported by the study of prehistoric bronze shields. These objects had universally been thought to be unfit for practical use since Coles' early experiments with replicas (Coles, 1962). However, the new research showed that not only were accurate replica shields effective in withstanding sword and spear attacks, but that the actual Bronze Age shields often display combat marks inflicted by swords, spears, and projectile points (Molloy, 2009; Uckelmann, 2011). Similar points were underscored by spear research, which revealed that these weapons might have been used in hybrid fighting styles that combined throwing, thrusting, and slashing moves (Anderson, 2011; Horn, 2013).

One of the most significant advances brought about by prehistoric weapon analysis concerns halberds (Fig. 2). This is a class of Early Bronze Age implements that had long been regarded as ceremonial due to supposed hafting weaknesses as well as a presumed clumsiness in the hand (O'Kelly, 1989: 164-5; Ó Ríordáin, 1937: 241). However, field tests with an Irish replica halberd disproved this view, since the weapon was shown to effectively pierce twenty sheep skulls without suffering any damage to its point, cutting edges, or hafting rivets (O'Flaherty, 2007a; 2007b). These results were further confirmed by the use-wear analysis of archaeological Irish, British, and continental halberds, which yielded plentiful evidence of blade-on-blade impact and other combat damage (Brandherm, 2003; 2004; 2011; Horn 2014; O'Flaherty et al., 2011). Copper-alloy arrow points from Iberia were also investigated using a similar method, which led to broadly similar results (Gutiérrez-Sáez et al., 2010; 2014). Overall, the wear analysis of Bronze Age weapons and armour, backed by a new generation of laboratory and field tests, has had a fundamental role in overturning

undemonstrated assumptions regarding the poor functional qualities of these objects, and ushered in a new era in the study of prehistoric interpersonal violence.

Metal tools have also received a good deal of scholarly attention, with particular reference to copper-alloy axes (Dolfini, 2011; Kienlin and Ottaway, 1998; Moyler, 2008; Roberts and Ottaway, 2003). This research revealed that the striation patterns visible on prehistoric axe-heads were largely caused by tree felling, wood working, and related activities (Fig. 3). Other sets of distinctive marks were also highlighted, which were caused by post-casting modifications of the objects including planishing, edge hardening, and sharpening. Overall, one of the greatest achievements of axe wear studies was to shift the research agenda towards the middle stage of the life-cycle of these objects. Previously, axe studies tended to focus on either production, with a strong emphasis on chemical analysis and metallography, or deposition, where purely archaeological narratives were prevalent. Wear analysis has now opened a window on the entire life-cycle of prehistoric axes, bringing to the fore an array of rich individualised biographies (Crellin, 2014; Crellin and Dolfini, 2013; Dolfini, 2011).

4.1 Research methodology

Although broadly based on the methodology applied to stone artefact analysis (Hayden, 1979; Keeley, 1980; Tringham et al., 1974; van Gijn, 2010; Vaughan, 1985), metalwork wear analysis has developed its own distinctive approach to research as a result of the disciplinary history and goals outlined above, and in response to the challenges posed by the material. Most of the analysts who have operated in the last fifteen years have deployed the three-stage protocol introduced by Kienlin and Ottaway (1998), which has been discussed above. This section offers a critical examination of each step while also discussing alternative approaches and practices.

4.2.1 Stage 1 – Experiments with replica objects

Conducting a meaningful experiment with replica copper-alloy objects normally involves the following steps: firstly, casting and building a complete, faithful replica of the objects to be tested; and secondly, designing a set of tests, which need to replicate as closely as possible the tasks and actions in which the archaeological objects are thought to have been used. This requires in-depth knowledge and understanding of the objects to be replicated including their chemical composition, casting process, post-casting treatment, and hafting materials and methods. It also forces researchers to make a number of educated guesses as to how long-disappeared components of the objects (e.g. the hafts) may have been built and connected to the metal blade or point, and how the complete objects may have been used, for what tasks, and with what tool and bodily motions (Fig. 4).

Kienlin and Ottaway's (1998) research on early metal axe-heads from the north-Alpine region provides a good example of the complexity of the task in hand. The authors first collated all compositional determinations of the archaeological axe-heads concerned and categorised them according to broad compositional groups. This allowed them to identify two main casting alloys (i.e. unalloyed copper and 6% tin-bronze), which they then used for their replicas. Secondly, they built sand moulds with the help of a wooden former and used

them to cast the axe-heads needed for the tests. Thirdly, they collated metallographic data from the literature, which guided them through the post-casting treatment of their replicas. In this instance, half the axe-heads were left as-cast and the other half were cold-worked to increase their hardness. Fourthly, the axe-heads were hafted according to two different methods, which were devised upon researching the literature for complete prehistoric tools. Fifthly, they designed a set of field tests, which entailed a number of choices regarding the tasks to be tested, the duration of each task, how to use the tool, and how to record and quantify data whilst in the field.

As is apparent from this review, designing a meaningful experiment for the production of reference wear marks is a complex procedure that requires in-depth archaeological and metallurgical knowledge, comprehensive research into the objects to be replicated, and a great number of conscious decisions, each of which will have some bearing on the traces produced during the tests. It also necessitates a degree of 'practical knowledge' and craft skill, which can only be achieved through protracted engagement with the objects (Doonan and Dungworth 2013). The design and implementation of meaningful experiments is an area in which metalwork wear analysis shows particularly close resonance with the methods used by researchers in lithic studies, and with the questions and difficulties they face.

4.2.2. Stage 2 – Taking the dental casts

Having generated suitable wear on the replica objects, casts may be taken using dental impression material. This normally involves the application of polyvinylsiloxane or similar silicon-based substances to the used portion of the objects (e.g. the cutting edge), which are then peeled off, bagged, labelled, and taken to the laboratory for examination. Likewise, dental casts can be taken from a sample of archaeological objects (Fig. 5).

A number of issues have emerged with this seemingly unproblematic procedure, which is employed as a matter of course in lithic microwear analysis. The first problem concerns the portion of the object to be analysed in relation to the research question. If the latter required the examination of the entire object (e.g. for determining manufacturing marks), the taking of dental casts would be either impractical or extremely expensive, thus limiting the quantity of the objects that could be analysed. Secondly, it was observed that the dental impression material may leave residual marks when used on light-coloured objects, and that fragments of the patina may be unwittingly removed from objects with substantial surface corrosion (Roberts and Ottaway, 2003: 123). For these reasons, some researchers dispensed with the dental casts altogether and conducted the analysis on the objects themselves, normally at museum premises (e.g. Dolfini 2011; Horn 2013; Lowe-Fri, 2011). The issue with staining and the removal of patina fragments emerged early in the history of the discipline and is often cited as a reason not to take dental casts. The problem seems to be caused by the incomplete mixing of the two parts of the silicon-based moulding compound, which has been eradicated by the development of accurate mixing guns. Recent geological research into the use of dental casting as a means to examine fossilised teeth from museum collections has provided quantitative evidence of the safety, accuracy and precision of some silicon-based moulding media (Goodhall et al., 2015). Similar tests are being carried out by the authors on prehistoric axe-heads, and it is hoped that they will conclusively prove the safety of the procedure for archaeological copper alloys.

For those analysts who work with the original objects in various museums, the utilisation of different microscopes may lead to inconsistent results, for example in image quality. This can be overcome by carrying one's own microscope to the museums. However, with the growing development of a wide range of new microscopes and techniques (see 5.2.1), it may be time to reconsider this problem as researchers may want to examine objects with types of microscopes not normally available at museums (Fig. 6). The bottom line here is that it has been ascertained that working with either the dental casts or the objects is practicable and safe under most circumstances; therefore it is up to the analyst to decide whether or not to take casts based on their own research goals, the objects with which they are working, and the preference of the museum curatorial staff.

4.2.3. Stage 3 – Examining wear on the dental casts or objects

The analysis of the dental casts or objects normally involves the examination of the traces under a low-power, incident-light microscope, working at magnification ranging from x5 to x50. The marks thus observed are then recorded on schematic diagrams, photographed using the microscope's mounted camera, characterised (e.g. as manufacturing, use, and post-depositional changes, or as plastic and physico-chemical deformations: Gutiérrez-Sáez and Martín-Lerma, 2015), and interpreted by reference to the experimental marks and the literature. Whilst working with the original objects, however, this protocol needs to be adjusted. For example, it is advisable to examine the objects visually and by means of a hand-held magnifier before they are put under the microscope. This allows a preliminary assessment of the wear marks including their location, nature and visibility in relation to the object's surface corrosion. Furthermore, additional light sources may be used (e.g. halogen desk lamps placed on either side of the microscope), which can be especially useful for highlighting faint traces (Dolfini, 2011). When working with the objects it is also important to devise identification and recording procedures that allow for the accurate positioning and cross-referencing of the marks observed. In our experience, the best way to do this is to sketch the objects prior to the analysis (Fig. 7). The sketches can be used to locate the marks and identify them through letters or numbers, which will then be reported on all the diagrams and notes compiled by the analyst. It is also crucial to take high-quality photographs and micrographs of the objects and marks, and cross-reference them with the sketches. Accurate recording is especially important to make analyses and results cross-comparable as well as to allow other researchers to assess, interpret, and perhaps critique one's results.

Although the analytical procedures discussed here have provided a fundamental reference point for most research undertaken in the last fifteen years, the eclectic strategies adopted by early scholars survived well into the new millennium, and still characterise the discipline to this day. These often encompass a broad spectrum of archaeological and metallurgical methods, which are used to complement the visual or microscopic characterisation of ancient metals. Alternative approaches are often deployed for the examination of combat or deliberate destruction marks, which can normally be assessed by the naked eye. They are also favoured in the study of large samples of objects, when painstaking detailed examination may be impractical (e.g. Brandherm, 2003; York, 2002; see also several chapters in Uckelmann and Mödinger, 2011). Other scholars attempted to quantify wear by drawing on the techniques employed by tribologists (e.g. Moyler, 2008). These approaches

add to the variety of the discipline and show that its fundamental principles and methods can be adapted to specific research questions and artefact classes.

5.1 Towards a manifesto for metalwork wear analysis

As this review shows, metalwork wear analysis is a fast-growing field of research. The last few years have seen the development of a shared approach to microscopic analysis as well as the first, systematic studies of a wide range of copper-alloy artefacts including swords, axe-heads, halberds, shields, spear-heads, and arrow points. However, if it is to grow for years to come, the discipline needs a robust injection of scientific rigour as well as an open debate regarding the analytical procedures, the experimental protocols, and the recording and interpretation strategies to be adopted. We discuss here the problems that, in our opinion, are to be addressed most urgently.

5.2.1 Formalisation of analytical protocols

Firstly, we need to formalise the analytical protocols pioneered so far to make them fully comparable with each other, and perhaps develop new ones for reflected-light, SEM, and quantitative analysis techniques. Two areas sorely need our attention: terminology and trace interpretation. Conflicting lists of terms have been proposed by various analysts, based on either causation or intensity of the damage, while others discriminate between plastic and physico-chemical deformations of the metal (e.g. Dolfini, 2011; Gutiérrez-Sáez and Martín-Lerma, 2015; Horn, 2013; O’Flaherty et al., 2011). This partly reflects different objects and uses, but it is partly due to personal preferences. Worryingly, the outcome is that different people call the same marks different names, or use the same names for different marks. This state of affairs hinders communication between analysts and research groups, and the problem needs to be addressed before the different terms crystallise further: clarity and consistency are essential pre-conditions to be able to talk to each other. As for trace interpretation, designing blind tests (e.g. Newcomer et al., 1986; Newcomer and Keeley, 1979; Rots et al., 2006; Stevens et al., 2010) specifically for copper alloys will ensure that we do not just call, but also understand the traces that we see in the same way as other researchers. Blind testing marked a fundamental step in the ‘loss of innocence’ of lithic microwear analysis (Evans, 2014) and we strongly advocate its application to metalwork analysis as well.

5.2.2 Understanding wear formation processes and the impact of corrosion

Secondly, we need to better understand wear formation and corrosion processes. This involves research into a number of problems including establishing more precisely and rigorously how marks such as edge chipping, plastic deformation and striations form, and how their shape and size relate to duration of use. Without such work the currently established methods will continue to lack a rigorous foundation. Sequential experiments (see Ollé and Maria Vergès, 2014) would be one way to address the problem as well as closer collaboration with material scientists and tribologists, who have long studied wear development mechanisms. In addition we need to investigate polishes, which are often visible on the cutting edges of metal tools and weapons but have seldom been studied (Fig. 8). Perhaps more urgently, we must address head-on the ‘elephant in the room’ of

metalwork wear analysis, which is understanding more precisely how post-depositional processes (and especially surface corrosion) affect the survival and visibility of wear traces (Gutiérrez-Sáez and Martín-Lerma, 2015). As for the relationship between alloy composition and wear formation, the studies hitherto conducted must be greatly expanded as to include further alloys, more classes of artefact, and a greater variety of edge-hardening treatments (Gutiérrez-Sáez and Soriano-Llopis, 2008; Soriano-Llopis and Gutiérrez-Sáez, 2009).

5.2.3 Higher magnifications and novel microscopic techniques

Thirdly, we need to test the potential of new types of microscopes and work at higher magnifications. At present, most practitioners start their analyses with hand lenses and then put the objects or dental casts under bi-focal low-power microscopes, whose magnifications rarely exceed x50. This procedure mirrors the early stages of lithic microwear analysis, until Keeley (1980) introduced a high-power approach (up to x400 magnification) based on reflected-light microscopy. Today both approaches are employed side by side by most lithic analysts as each has its own strengths and limitations (Marreiros et al., 2015). The time has now come for metalwork researchers to do the same, and test the potential of high-power microscopy including Scanning Electron Microscopes (e.g. Borel et al., 2014, Tumung et al., 2015), Focal Variation Microscopes/3-Dimensional Microscopes (e.g. Bello, et al., 2009; Bello et al., 2011; Bello et al., 2013 Macdonald, 2014), and Laser Scanning Confocal Microscopes (e.g. Evans and Donahue, 2008; Ibáñez et al., 2014) on copper alloys. In particular, we need to understand what new traces can be identified with high-power microscopes and if the latter allow a better resolution of wear, e.g. distinguishing between traces caused by different materials. Given the fundamental role that high-power microscopy has had in addressing these problems in lithic microwear analysis, one could presume that significant gains can be made in metalwork studies as well.

5.2.4 Formalised experimental protocols

Fourthly, there is a real and pressing need to develop formalised experimental protocols for our tests with replica objects. Two contrasting approaches have been tried so far: laboratory tests and field tests. Conducting laboratory tests with rigs or robotic devices offers the distinctive advantage of a controlled environment, in which all factors contributing to wear formation can more easily be monitored, recorded, and understood. Yet the drawback is that the complexity of human behaviour can rarely be reproduced by a robot or a rig. On the contrary, field tests provide us with an opportunity to experiment with objects in seemingly 'authentic' conditions (Kampaus, 2006: 121), but control of wear formation processes can be poor. Moreover, reproducing 'authentic' use conditions for tests with ancient tools and weapons may be trickier than it first appears. Objects often give us some indication as to how they might be used insofar as their style inheres in their function (Shanks and Tilley 1987: 92); in the case of a pen, for instance, it is obvious which end is for writing. Yet the use of an object is predicated upon a relational synergy between a particular knowing body and the particular object at a given moment in time. Muscle memories and structures emerge in conjunction with our interactions with things and come to shape how we relate to the material world more broadly. One may use an object in a manner that was unthought-of during production, or with a novel bodily technique: consider those who write and paint with the pen in their mouths. Even though an object may imply how it is best used, nuances within that use (e.g. left and right handedness) and the creativity that emerges from the

relational nexus of people and objects may be especially hard to grasp under certain circumstances, or when dealing with long-disappeared objects. It follows that reconstructing socially specific 'techniques of the body' (Mauss, 1973) may occasionally prove difficult; the past, as Lowenthal (1985) perceptively put it, is a foreign country. A way out of the problem is offered by multivocal approaches to experimentation, in which the conditions and factors underpinning the tests are meaningfully varied (Bell, 2015; Hurcombe, 2008). This is, for example, the approach chosen for the ongoing Newcastle Bronze Age Combat Project (Fig. 9), which combines two different sets of tests with replica weapons in order to assess the formation of combat marks in varied circumstances (Crellin et al., 2015). Whatever pathway to experimentation one may select, it is important that tests with replica objects are at once more reflexive and more formalised. As with all archaeological experiments, our tests must address specific research questions, lay out a clear methodology in which all variables should be discussed (and possibly controlled), and enable us to critically evaluate the results against the archaeological record (Cunningham et al., 2008; Outram, 2008).

5.2.5 Expanding the range of materials and objects

Fifthly, we need to extend wear analysis beyond copper alloys and prehistoric tools and weapons from Europe. These materials and objects have hitherto dominated the subject but there is ample scope for expansion beyond them. For example, the method could easily be adapted to the examination of well-preserved historic and ethnographic iron and steel objects in order to address research problems concerning their manufacture, use, and artefact biographies including repairs and conservation. As for the more corroded archaeological iron and steel artefacts, these could afford quantitative approaches to analysis of the kind used in tribology (Moyler, 2008). Moreover, copper alloys are a prominent class of material culture in the Americas and there is great potential for research in this region as well as elsewhere across the world. One also has to consider the untapped potential of residue analysis as mineralised organic residues often survive on the oxidised surface of copper alloys. Mineralised residues have yielded vital information concerning prehistoric textiles and tools' and weapons' hafts (Gutiérrez-Sáez and Martín-Lerma, 2015: 184). Curiously, however, these studies have mostly been conducted disjointed from wear analysis, and greater integration between disciplines is called for here. As our knowledge of wear formation as well as our analytical methods become increasingly formalised and rigorous, there is a genuine opportunity to expand the discipline beyond European prehistoric research and to have a far wider impact on global archaeology.

5.2.6 Sharing databases of experimental marks

Finally, there is a real need for practitioners in the field to share the research methods and results more broadly than has been done so far. One of the obvious ways of doing so is to develop reference databases of archaeological and experimental traces, which could be made available to all practitioners online (e.g. via the UK-based Archaeology Data Services: <http://archaeologydataservice.ac.uk/>). This is an area in which metalwork analysis could lead the way within broader wear studies. The current practice of developing a personal research reference collection, widespread in lithic traceology, is frankly wasteful and unwittingly diminishes the scientific worth of individual research by reducing comparability. If reference collections were available online it would be much easier for analysts to compare their results and to check that they are calling the same marks the same names.

The issue is all the more important for metalwork wear analysis as replicas tend to be expensive. Sharing our results and the data behind our interpretations is good science as it leaves space for others to truly understand, critique, and debate our results and interpretations.

6.1 Conclusion

As recently as 2006, Kampaas (2006: 119-20) wrote that “the future of archaeometallurgical usewear is not certain, as it is being conducted by a small group of scholars, associated with a limited number of universities”. The wealth of research undertaken since shows that the future of metalwork wear analysis no longer hangs in the balance. The discipline has taken root at several universities across Europe, is practised by a growing number of scholars, and has developed its own distinctive approaches to research. It is also taught in a Master’s module at Newcastle University (UK), which provides formal training for the next generation of scholars. However, the subject has yet to see the growing pains that lithic microwear analysis once suffered, which marked its coming of age. This article has highlighted the problems on which metalwork wear analysis needs to focus so that it too can lose its early innocence. Importantly, these problems straddle and intersect the fields of microwear analysis, archaeometallurgy, and experimental archaeology. It logically follows that researchers must achieve a good knowledge and understanding of all three subjects, without necessarily being specialists in any of them. Hence, we maintain that metalwork wear analysis ought to position itself at the nexus between microwear analysis, archaeometallurgy, and experimental archaeology, since all three subjects contribute to it in equal proportion (Fig. 10). As most current practitioners have a background in metallurgical studies and European prehistory, reaching this ideal balance point involves a collective journey towards the fields of microwear analysis and experimental archaeology. Here lies what is perhaps the greatest challenge for the next decade. For it is only by completing this journey that metalwork wear analysis can fulfil its potential of enlivening an entire category of objects from our past, not only by answering some of the ‘big’ questions of archaeology, but also by asking new and exciting ones.

Word count: 5,475

End notes

- (1) We are not considering here the wealth of information that can be gleaned from the analysis of the internal structure of the object by means of x-raying, 3D computer tomography, metallography, and other techniques of structural and crystallographic analysis.

Caption List

Fig. 1 – Combat tests with replica Bronze Age swords and shields. Experiential tests of this kind have led to a wholesale reappraisal of the fighting potential and uses of prehistoric metal weaponry (from Molloy 2009). *Half Column Width*

Fig. 2 – Prehistoric halberd blade from Italy. Prehistoric halberds from Europe often display distinctive marks on the cutting edges (see inset, x12 magnification), which are interpreted as evidence of blade-on-blade strike in combat encounters (photo: A. Dolfini, reproduced by courtesy of the Soprintendenza per i Beni Archeologici della Toscana). *Full Column Width*

Fig. 3 – Early Bronze Age Flat Axe from the Manx Museum on the Isle of Man. The photo and micrograph showing striations from both wear and re-sharpening to the blade. (photo: R. Crellin, with permission of Manx National Heritage). *Full Column Width*

Fig. 4 – Newcastle student Joshua Desrosier fells a birch tree with a replica Middle Bronze Age palstave. Designing meaningful experiments with replicas forces researchers to make educated guesses regarding construction technology and the uses of prehistoric objects (photo: A. Dolfini). *Half Column Width*

Fig. 5 – Taking a cast of an experimental axe blade using high-precision impression material (photo: A. Dolfini). *Half Column Width*

Fig. 6 – Wear marks on a range of copper-alloy objects. *Top left*: Use-wear marks on the surface of a Late Bronze Age sword from the Yorkshire Museum of Archaeology (bar length – 10mm, photo: R. Hermann). *Top right*: Spear stab mark on the surface of a replica bronze shield (bar length – 2mm; photo: R. Crellin). *Lower left*: Bending and notching to the blade of a flanged Early Bronze Age axe from the Manx Museum, Isle of Man (bar length – 2cm, photo: R. Crellin, with permission of Manx National Heritage). *Lower right*: Notch to the blade of a replica spearhead caused by a sword blade (bar length – 2mm, photo: R. Crellin). *Full Column Width*

Fig. 7 – Annotated digitised sketch of a replica axe. Figures in blue circles relate to observed wear marks, figures in red boxes indicate the position and number of associated micrographs (illustration: R. Crellin). *Full Column Width*

Fig. 8 – Short perpendicular striations associated with localised polish on the cutting edge of a copper-alloy axe-heads from the Tyne and Wear Archives and Museums collections, Newcastle upon Tyne. Although frequently observed, the use-related polish found on ancient metalwork has hitherto received little attention from analysts (bar length: 0.5mm; photo: J. Desrosier, by courtesy of the Society of Antiquaries of Newcastle upon Tyne). *Half Column Width*

Fig. 9 – Field tests with replica swords within the Newcastle Bronze Age Combat project. Problem-oriented test design and a clear methodology are essential components of any experiments aiming to understand wear formation processes (photo: D. Horan). *Half Column Width*

Fig. 10 – It is maintained in this article that metalwork wear analysis ought to position itself at the disciplinary intersection between microwear analysis, archaeometallurgy, and experimental archaeology (drawing: A. Dolfini). *Half Column Width*

Acknowledgements

The authors thank the Tyne and Wear Archives and Museums for allowing wear analysis of the objects in their care. We are especially grateful to Andrew Parkin and Joanne Anderson for facilitating the borrowing of the objects. We also thank Barry Molloy for commenting upon an earlier draft of this article. The authors wish to thank Raphael Hermann, David Horan and Joshua Desrosier for allowing images from their joint research projects to be reproduced here. Andrea wishes to acknowledge his Master's students, whose thoughtful observations and work helped to delineate some of the problems and opinions expressed here. Rachel's research for this paper is funded by a Leverhulme Early Career Research Fellowship (ECF-2014-122). All opinions and errors rest with the authors.

Reference List

- Anderson, K. 2011. Slashing and thrusting with Late Bronze Age spears: analysis and experiment. *Antiq* 85, 599-612.
- Bell, M. 2015. Experimental archaeology at the crossroads: a contribution to interpretation or evidence of 'xeroxing'? in: Chapman, R. and Wylie, A. (Eds.), *Material Evidence: Learning from archaeological practice*. Routledge: London and New York, pp. 42-58.
- Bello, S.M. Parfitt, S.A., Stringer, C. 2009. Quantitative micromorphological analyses of cut marks produced by ancient and modern handaxes. *J. Archaeol. Sci.* 36, 1869–1880.
- Bello, S.M., Vervenioutou, E., Cornish, L., Parfitt, S.A. 2011. 3-Dimensional Microscope Analysis of Bone and Tooth Surface Modifications: comparisons of fossil specimens and replicas. *Scanning* 33, 316–324.
- Bello, S.M., De Groote, I., Delbarre, G. 2013. Application of 3-dimensional microscopy and micro-CT scanning to the analysis of Magdelaenian portable art on bone and antler. *J. Archaeol. Sci.* 40, 2464–2476.
- Borel, A., Ollé, A., Maria Vergès, J., Sala, R. 2014. Scanning Electron and Opital Light Microscopy: two complementary approaches for the understanding and interpretation of usewear and residues on stone tools. *J. Archaeol. Sci.* 48, 46–59.
- Brandherm, D. 2003. *Die Dolche und Stabdolche der Steinkupfer- und Älteren Bronzezeit auf der Iberischen Halbinsel* (Prähistorische Bronzefunde VI, 12). Stuttgart: Franz Steiner.
- Brandherm, D. 2004. Porteurs de hallebardes? Überlegungen zur Herkunft, Entwicklung und Funktion der bronzezeitlichen Stabklingen. In: H.-J. Beier, R. Einicke (Eds.), *Varia Neolithica* III, pp. 279–334.
- Brandherm, D. 2011. Use-wear on Bronze Age halberds: the case of Iberia. In: Uckelmann, M., Mödlinger, M. (Eds.) *Warfare in Bronze Age Europe: Manufacture and Use of Weaponry*. Oxford: Archaeopress, pp23-38.
- Bridgford, S.D. 1997. Mightier than the pen? An edgewise look at Irish Bronze Age swords. In: Carman, J. (Ed.) *Material Harm: Archaeological Studies of War and Violence*: Glasgow: Cruithne Press, pp. 95-115.
- Bridgford, S.D. 2000. *Weapons, warfare and society in Britain 1250-750 BC*. Unpublished PhD Thesis. Sheffield: University of Sheffield.

- 550 Clark, D. 1973. Archaeology: the loss of innocence. *Antiquity* 47 (185), 6–18.
- 551 Coles, J.M. 1962. European Bronze Age shields. *Proc. of the Prehistoric Society* 28, 156-190.
- 552 Crellin, R.J. 2014. Changing Times: the emergence of a Bronze Age on the Isle of Man.
553 Unpublished PhD Thesis, Newcastle University.
- 554 Crellin, R.J., Dolfini, A. 2013. Metals under the microscope: use-wear analysis of prehistoric
555 copper alloy objects. Paper delivered in the 'Novel approaches of microscopy and
556 microanalysis' session at the SAA 2013 Meeting in Honolulu, Hawaii, USA.
- 557 Crellin, R.J., Dolfini, A., Uckelmann, M., Hermann, R. 2015. Unlocking Bronze Age combat:
558 Field experiments and use-wear analysis. Paper delivered in the 'Quantitative and
559 qualitative approaches to prehistoric warfare' session at the EAA 2015 Meeting in Glasgow,
560 UK.
- 561 Cunningham, P., Heeb, J., Paardekooper, R. 2008. Introduction. In: Cunningham, P., Heeb, J.
562 and Paardekooper, R. (Eds.), *Experiencing Archaeology by Experiment*. Oxbow: Oxford, pp. v-
563 ix.
- 564 Dolfini, A. 2011. The function of Chalcolithic metalwork in Italy: An assessment based on
565 use-wear analysis. *J. Archaeol. Sci.* 38(5), 1037-1049.
- 566 Donhaue, R.E. 1994. The current state of lithic microwear research. In: Ashton, N. and David,
567 A. (Eds.), *Stories in Stone*. London: Lithic Studies Society, pp. 156-168.
- 568 Doonan, R.C.P., Dungworth, D. 2013. Experimental archaeometallurgy in perspective. In
569 Dungworth, D., Doonan, R.C.P. (Eds.), *Accidental and Experimental Archaeometallurgy*.
570 London: The Historical Metallurgy Society, pp. 1-10.
- 571 Evans, A.A. 2014. On the importance of blind testing in archaeological science: the example
572 from lithic functional studies. *J. Archaeol. Sci.* 48, 5–14.
- 573 Evans, A., Donahue, R. (2008). Laser scanning confocal microscopy: A potential technique for
574 the study of lithic microwear. *J. Archaeol. Sci.* 35, 2223–2230.
- 575 Fullagar, R., Matheson, C. 2014. Stone tool usewear and residue analysis. In Smith, C. (Ed.),
576 *Encyclopaedia of Global Archaeology*, New York: Springer, pp. 7062-7065.
- 577 Goodall, R.H., Darras, L.P., Purnell, M.A. 2015. Accuracy and precision of silicon based
578 impression media for quantitative areal texture analysis. *Scientific Reports* 5, 10800. DOI:
579 10.1038/srep10800.
- 580 Gordon, R.B. 1985. Laboratory evidence of the use of metal tools at Machu Picchu (Peru)
581 and environs. *J. Archaeol. Sci.* 12, 311-327.
- 582 Gosden, C., Marshall, Y. 1999. The Cultural Biography of Objects. *World Archaeol.* 31 (2),
583 169–178.
- 584 Gutiérrez-Sáez, C., Martín-Lerma, I. 2015. Traceology on metal. Use-wear marks on copper-
585 based tools and weapons. In: Marreiros, J., Gibaja, J.F., Bicho, N. (Eds.), *Use-Wear and*
586 *Residue Analysis in Archaeology*. New York: Springer, pp. 171-188.

- 587 Gutiérrez-Sáez, C., Soriano-Llopis, I. 2008. La funcionalidad sobre material metálico: bases y
588 aplicaciones de estudio. In: Rovira-Llorens, S., García-Heras, M., Gener-Moret, M., Montero-
589 Ruíz, I. (Eds.) *VII Congreso Ibérico de Arqueometría*. Madrid: Quadro, pp. 432-447.
- 590 Gutiérrez-Sáez, C., López del Estal, A., Simón-Martín, A., Muñoz-Moro, P., Bashore-Acero,
591 Ch., Chamón-Fernández, J., Martín-Lerma, I., Sanz-Salas, E., Pardo-Naranjo, A. I., Marín de
592 Espinosa, J. A. 2010. Puntas de Palmela: procesos tecnológicos y experimentación. *Trabajos*
593 *de Prehistoria*, 67(2), 405–428.
- 594 Gutiérrez-Sáez, C., Martín-Lerma, I., López Del Estal, A., Bashore-Acero, Ch. 2014. *The*
595 *functionality of Palmela points as throwing weapons and projectiles. Use-wear marks*. In:
596 Marreiros, J., Bicho, N., Gibaja J.F. (Eds.), *International Conference on Use-Wear Analysis*.
597 Cambridge: Cambridge Scholars, pp. 442-456.
- 598 Hayden, B., 1979. *Lithic Use-Wear Analysis*. Academic Press, London.
- 599 Horn, C. 2013. Weapons, fighters and combat: spears and swords in Early Bronze Age
600 Scandinavia. *Danish J. Archaeol.* 2013, 1-25.
- 601 Horn, C. 2014. *Studien zu den Europäischen Stabdolchen*. Habelt Verlag: Bonn.
- 602 Hurcombe, L. 2008. Organics from inorganics: using experimental archaeology as a research
603 tool for studying perishable material culture. *World Arch.* 40(1), 83–115.
- 604 Ibáñez, J.J., González-Urquijo, J.E., Gibaja, J. 2014. Discriminating wild vs domestic cereal
605 harvesting micropolish through laser confocal microscopy. *J. Archaeol. Sci.* 48, 96–103.
- 606 Kamphaus, B. 2006. Usewear and functional analysis of bronze weapons and armor. *J. World*
607 *Anthropology: Occasional Papers III.1*, 113-38.
- 608 Keeley L. 1980. *Experimental determination of stone tool uses: A microwear analysis*.
609 Chicago: University of Chicago Press.
- 610 Keeley, L.H. 1996. *War before civilization*. Oxford: Oxford University Press.
- 611 Kienlin, T.L., Ottaway, B.S. 1998. Flanged axes of the north-alpine region: an assessment of
612 the possibilities of use-wear analysis on metal artefacts. In: Mordant, C., Perno, M., Rychner,
613 V. (Eds.) *L'Atelier du bronzier en Europe du XX au VIII siècle avant notre ère*, vol. II. Paris:
614 Comité des travaux historiques et scientifique, pp. 271-286.
- 615 Kristiansen, K. 1978. The consumption of wealth in Bronze Age Denmark. A study in the
616 dynamics of economic processes in tribal societies. In K. Kristiansen, C. Paludan-Müller (eds.)
617 *New Directions in Scandinavian Archaeology*. Copenhagen: The National Museum of
618 Denmark, pp. 158-190.
- 619 Kristiansen, K. 1984. Krieger und Häuptlinge in der Bronzezeit Dänemarks: Ein Beitrag zur
620 Geschichte des Bronzezeitlichen Schwertes. *Jahrbuch des Römisch-Germanischen*
621 *Zentralmuseums* 31, 187-208.
- 622 Kristiansen, K. 2002. The tale of the sword: swords and swordfighters in Bronze Age Europe.
623 *Oxford J. Archaeol.* 21(4), 319-332.

- 624 Lowe-Fri, M. 2011. *The Double Axe in Minoan Crete: A Functional Analysis of Production and*
625 *Use*. Bar Int. Ser. 2304. Oxford: Archaeopress.
- 626 Lowenthal, D. 1985. *The Past is a Foreign Country*. Cambridge: Cambridge University Press.
- 627 Macdonald, D. A. 2014. The application of focus variation microscopy for lithic use-wear
628 quantification. *J. Archaeol. Sci.* 48, 26–33.
- 629 Marreiros, J., Mazzucco, N., Gibaja, J.F., Bicho, N. 2015. *Macro and micro evidences from the*
630 *past: the state of the art of archaeological use-wear studies*. In: Marreiros, J., Gibaja, J.F. and
631 Bicho, N. (eds.), *Use-Wear and Residue Analysis in Archaeology*. New York: Springer, pp. 5-
632 26.
- 633 Mauss, M. 1973. Techniques of the body. *Economy and Society* 2(1), 70–88.
- 634 Mödlinger, M. 2011. Ritual object or powerful weapon? The usage of central Europe Bronze
635 Age swords. In: Uckelmann, M., Mödlinger, M. (Eds.) *Warfare in Bronze Age Europe:*
636 *Manufacture and Use of Weaponry*. Oxford: Archaeopress, pp. 153-166.
- 637 Molloy, B. 2007. What's the bloody point? Fighting with Irish Bronze Age weapons. In: B.
638 Molloy (Ed.) *The Cutting Edge: studies in ancient and medieval combat*. Stroud: Tempus, pp.
639 90-111.
- 640 Molloy, B. 2008. Martial arts and materiality: a combat archaeology perspective on Aegean
641 swords of the fifteenth and fourteenth centuries BC. *World Archaeol.* 40(1), 116-134.
- 642 Molloy, B. 2009. For Gods or Men? A reappraisal of the function of European Bronze Age
643 shields. *Antiq.* 83, 1052-1064.
- 644 Molloy, B. 2010. Swords and swordsmanship in the Aegean Bronze Age. *American J.*
645 *Archaeol.* 114(3), 403-428.
- 646 Molloy, B. 2011. Use-wear analysis and use-patterns of Bronze Age swords. In: Uckelmann,
647 M., Mödlinger, M. (Eds.) *Warfare in Bronze Age Europe: Manufacture and Use of Weaponry:*
648 Oxford: Archaeopress, pp 67-84.
- 649 Moyler, S. 2008. Doing away with dichotomies? Comparative use-wear analysis of Early
650 Bronze Age axes from Scotland. In: Hamon, C., Quilliec, B. (Eds.) *Hoards from the Neolithic to*
651 *the Metal Ages: Technical and Codified Practices* (BAR Int. Ser. S1758). Oxford:
652 Archaeopress, pp. 79-90.
- 653 Newcomer, M.H., Keeley, L.H., 1979. Testing a method of microwear analysis with
654 experimental flint tools. In: Hayden, B. (Ed.), *Lithic Use-wear Analysis*. Academic Press, New
655 York, pp. 195–205.
- 656 Newcomer, M., Grace, R., Unger-Hamilton, R., 1986. Investigating microwear polishes with
657 blind tests. *J. Archaeol. Sci.* 13, 203–217.
- 658 Odell, G. 2004. *Lithic analysis*. New York: Kluwer.
- 659 O’Flaherty, R. 2007a. A weapon of choice: experiments with a replica Irish Early Bronze Age
660 halberd. *Antiq.* 81, 423-434.

- 661 O'Flaherty, R. 2007b. The Irish Early Bronze Age halberd: practical experiment and combat
662 possibilities. In: B. Molloy (Ed.) *The Cutting Edge: studies in ancient and medieval combat*.
663 Stroud: Tempus, pp. 77-89.
- 664 O'Flaherty, R., Gilchrist, M.D., Cowie, T. 2011. Ceremonial or deadly serious? New insights
665 into the function of Irish Early Bronze Age Halberds. In: Uckelmann, M., Mödinger, M. (Eds.)
666 *Warfare in Bronze Age Europe: Manufacture and Use of Weaponry*. Oxford: Archaeopress,
667 pp. 39-52.
- 668 O'Kelly, M.J. 1989. *Early Ireland*. Cambridge: Cambridge University Press.
- 669 Ó Ríordáin, S.P. 1937. The halberd in Bronze Age Europe. *Archaeologia* 86, 195-321.
- 670 Ollé, A., Maria Vergès, J. 2014. The use of sequential experiments and SEM in documenting
671 stone tool microwear. *J. Archaeol. Sci.* 48, 60–72.
- 672 Outram, A. 2008. Introduction to experimental archaeology. *World Arch.* 40(1), 1–6.
- 673 Penman, J. 1977. The Old Copper culture: an analysis of Old Copper artifacts. *The Wisconsin*
674 *Archeologist* 58(1), 3-23.
- 675 Quilliec, B.T. 2008. Use, wear and damage: treatment of bronze swords before deposition.
676 In: Hamon, C., Quilliec, B. (Eds.) *Hoards from the Neolithic to the Metal Ages: Technical and*
677 *Codified Practices* (BAR Int. Ser. S1758). Oxford: Archaeopress, pp. 67-78.
- 678 Roberts, B., Ottaway, B.S. 2003. The use and significance of socketed axes during the Late
679 Bronze Age. *European J. Archaeol.* 6(2), 119-140.
- 680 Rots, V., Pirnay, L., Pirson, P., Baudoux, O., 2006. Blind tests shed light on possibilities and
681 limitations for identifying stone tool prehension and hafting. *J. Archaeol. Sci.* 33, 935–952.
- 682 Schauer, P. 1979. Eine urnenfelderzeitliche Kampfweise. *Archäologisches*
683 *Korrespondenzblatt* 9(1), 65-87.
- 684 Semenov, S.A., 1964. *Prehistoric Technology: An Experimental Study of the Oldest Tools and*
685 *Artefacts from Traces of Manufacture and Wear*. Cory, Adams and Mackay, London.
- 686 Shanks, M., Tilley, C. 1987. *Social Theory and Archaeology*. Cambridge: Polity Press.
- 687 Soriano-Llopis, I., Gutiérrez-Sáez, C., 2009. Use-wear analysis on metal: the influence of raw
688 material and metallurgical production processes. In: *Archaeometallurgy in Europe,*
689 *Proceedings of the 2nd Conference (Aquileia 2007)*. Milano: Associazione Italiana di
690 Metallurgia, pp. 115–124.
- 691 Stevens, N.E., Harro, D.R., Hicklin, A., 2010. Practical quantitative lithic use-wear analysis
692 using multiple classifiers. *J. Archaeol. Sci.* 37, 2671–2678.
- 693 Tringham, R. Copper, G., Odell, G., Voytek, B., Whitham, a. 1974. Experimentation in the
694 formation of edge damage: a new approach to lithic analysis. *J. Field Archaeol.* 1, 171–196.
- 695 Tumung, L., Bazgir, B., Ollé, A. 2015. Applying SEM to the study of use-wear on unmodified
696 shell tools: an experimental approach. *J. Archaeol. Sci.* 59, 179–196.

- 697 Uckelmann, M., 2011. The function of Bronze Age shields. In: Uckelmann, M., Mödlinger, M.
698 (Eds.) *Warfare in Bronze Age Europe: Manufacture and Use of Weaponry*. Oxford:
699 Archaeopress, pp. 187-199.
- 700 Uckelmann, M., Mödlinger, M. (Eds.). 2011. *Warfare in Bronze Age Europe: Manufacture*
701 *and Use of Weaponry*. Oxford: Archaeopress.
- 702 Van Gijn, A. 2010. *Flint in Focus*. Leiden: Sidestone Press.
- 703 Vaughan, P., 1985. *Use-Wear Analysis of Stone Tools*. University of Arizona Press, Tucson.
- 704 Wall, J. 1987. The role of daggers in Early Bronze Age Britain: the evidence of wear analysis.
705 *Oxford J. Archaeol.* 6(1), 115-118.
- 706 York, J. 2002. The life cycle of Bronze Age metalwork from the Thames. *Oxford J. Archaeol.*
707 21(1), 77-92.